

Long Term Durability of Pozzolanic Cement Concretes in Severe Environments

A.A. Ramezaniapour¹, A.R. Pourkhorshidi², A.M. Ramezaniapour³
¹*Amirkabir University of Technology, Tehran, IRAN,* ²*Building and
Housing Research Centre, Tehran, IRAN;* ³*University of Toronto,
Canada*

ABSTRACT

Corrosion of reinforced concrete structures is a major problem in the hot and corrosive environments of the Persian Gulf region. The use of special cements and pozzolans in corrosive regions, has shown desirable performance of reinforced concrete and enhanced the durability of concrete. Results of accelerated tests in simulated environments show that supplementary cementing materials can enhance the durability of concrete.

In the present investigation, concrete specimens containing different supplementary cementing materials, namely; silica fume, slag, trass as a natural pozzolan and mixtures of cement and two pozzolans have been thoroughly tested. The test conducted include, compressive strength, permeability, chloride diffusion, corrosion of reinforcing bars and carbonation depth, all at different ages. The variables were cement types, supplementary cementing materials, water cement ratio and cover thicknesses. After standard curing, concrete specimens were transferred to the Persian Gulf region and maintained in submerged, wetting and drying and coastal environments.

Results of four year tests are presented in this paper. With respect to the alternate cycles of wetting and drying known as most severe condition, the superior performance of silica fume was followed by the mixtures of two supplementary cementing materials. However all concrete mixtures containing natural or artificial pozzolans showed better performance when compared with the plain cement control concrete mixtures.

Keywords: corrosion, durability, natural pozzolan, silica fume, slag

1- INTRODUCTION

Concrete deterioration and corrosion of reinforced concrete structures is a major problem in the hot and corrosive environments of the Persian Gulf region. Because of ever-increasing and multilateral development for the sake of the marine transit and the operation and extraction of oil and gas resources, there is a substantial need for the construction of

durable concrete structures in this region. Survey of newly built and old concrete structures in the Persian Gulf region show that many of these structures are not able to satisfy their minimum service life [1]. However, the use of special cements and pozzolans in corrosive regions, has shown desirable performance of reinforced concrete and enhanced the durability of concrete [2-5]. Results of accelerated tests in simulated environments show that supplementary cementing materials can enhance the durability of concrete [6].

Attempt have been made to investigate the long term performance of concretes containing supplementary cementing materials in severe environments. The objective of these investigations is to create models for the prediction of service life of concrete structures and establish e model code for design [7-8]. In order to establish such models on the basis of long term tests in severe environments, the following research project was conducted. Concrete

2-EXPERIMENTAL PROGRAM

2-1-Materials

Cement - ASTM Type II portland cement and ASTM Type V portland cement was used in this investigation.

Slag - slag-modified portland cement (I (SM) in accordance with ASTM C 595) was incorporated in the mixtures.

Pozzolan- Trass as a natural pozzolan was used in this program.

Silica fume (micro silica)- A locally produced silica fume (in accordance with ASTM C 1240) was used. The chemical composition of the cements and pozzolans are given in Table 1.

Table. 1. Chemical compositions of cements and cement replacement materials

	Type II	Type V	Slag	Trass	Silica fume
SiO ₂	20.96	21.47	23.08	24.24	95.1
Al ₂ O ₃	4.2	3.95	5.5	4.25	0.6
Fe ₂ O ₃	4.6	4.4	3.4	3.8	1.1
MgO	3.4	2.3	3.4	3.8	0.6
CaO	61.88	63.84	60.2	58.8	1.02
SO ₃	1.79	2.17	2.64	3.82	1.2
Na ₂ O+0.658 K ₂ O	1.47	1.01	1.08	1.26	-
C ₃ S	52.74	57.72	-	-	-
C ₂ S	20.31	18.01	-	-	-
C ₃ A	7.35	3.02	-	-	-

Aggregates- Crushed gravels and sand were used as coarse and fine aggregates, respectively. The properties of aggregates are shown in Table 2.

Table. 2. Aggregate properties

	Specific Gravity	Absorption (%)	Fineness Modulus
Sand	2.53	2.6	2.7
Gravel	2.56	1.46	6.5

Superplasticizer- The superplasticizer was a conventional melamine-based admixture with a solids content of 40% and a pH of 8.

Steel Reinforcing Bars- The steel reinforcing bars met the requirements of Grade 60 of ASTM A 615/A 615 M.

2-2- Concrete Mixtures

Mixture proportions of concrete are summarized in Table 3. Water-cementitious materials ratios(w/cm) were 0.35 and 0.4. The slump of the fresh concretes was kept between 5 to 8 cm and air content between 3 to 5%. 10x10x10 cm cubes were used for compressive strength and permeability tests. For carbonation test, 15x15x60 cm plain concrete specimens were used. In order to measure the corrosion potential, electrical resistance, and current density, steel bars and stirrups were embedded at cover depths of 3.5, 5, and 7 cm (see Fig. 1).

After casting, all the specimens were covered with water-saturated burlap and plastic sheets. The specimens were moist cured for 7 days, followed by 14 days of air drying. Following this, the specimens were transported to the Persian Gulf region and exposed in different conditions, namely in the air, in coastal area, tidal region of the sea (cycling wetting and drying), and submerged in the sea. Control unreinforced specimens of each mixture were kept in standard laboratory curing conditions.

Table. 3. Mixture proportions

Mixture	Cement type	CRM type	w/cm	Water (kg)	Cement (kg)	CRM (kg)	Sand (kg)	Gravel (kg)
A1	Type II	-	0.40	160	400	-	760	1050
A2	Type II	-	0.35	140	400	-	760	1050
B1	TypeV	-	0.40	160	400	-	760	1050
B2	Type V	-	0.35	140	400	-	760	1050
C1	Type II	Silica fume	0.40	160	372	28	760	1050
C2	Type II	Silica fume	0.35	140	372	28	760	1050
D1	Trass	-	0.40	160	400	-	760	1050
D2	Trass	-	0.35	140	400	-	760	1050
E1	Slag	Silica fume	0.40	160	380	20	760	1050
E2	Slag	Silica fume	0.35	140	380	20	760	1050

3- TEST METHODS

Half-cell potential (Ag/AgCl), polarization resistance, and cover concrete resistance were measured by a portable corrosion measurement device. Polarization resistance and concrete resistance were measured by DC impedance technique (Galvanostatic Pulse

Technique). The applied currents were normally in the range of 10 to 100 μA and the typical pulse durations were between 5 to 30 seconds. Micro-cell corrosion current was estimated based on the measured polarization resistance using the following expression:

$$I_{corr} = \frac{B}{R_P}$$

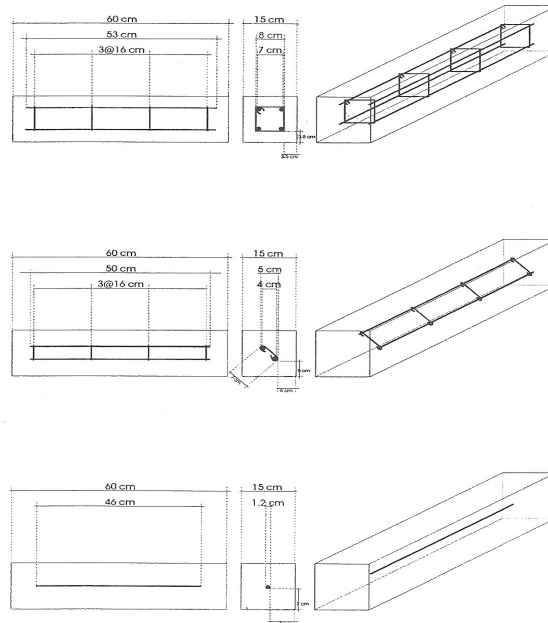


Fig. 1. Schematic of the specimens for measurement of corrosion

Where, I_{corr} = the micro-cell corrosion current density in $\mu\text{A}/\text{cm}^2$. B = an empirical constant assumed to be 25 mV for actively corroding steel and 50 mV for passive steel. R_P = the polarization resistance.

Carbonation depth of the specimens was measured by spraying a 1% phenolphthalein solution on freshly cut surfaces.

Acid soluble chloride-ion concentrations were determined at depths 0~10, 10~20, 20~30, 30~40, and 40~50 mm in accordance with ASTM C1152/C 1152M-97 test method.

The compressive strength and permeability of concrete mixtures under water pressure were measured for control concrete specimens.

4- RESULTS AND DISCUSSIONS

4-1- Corrosion Potential, Electrical Resistance, and Micro-cell Corrosion

The corrosion potential, concrete electrical resistance, and micro-cell current density were measured at 1 and 4 years. Test results are illustrated in Tables 4-8 and Figs. 2-9.

For the tidal region, concretes made with ASTM Type V cement, and slag cement with 5% silica fume showed more negative potentials. For concretes with ASTM Type II cement, Type II with 7% silica fume, and trass cement, less negative potentials were observed. Higher current density and lower electrical resistance were observed for the specimens made with ASTM Type V cement and cover thicknesses of 3.5 and 5 cm, when compared with other specimens. For these concrete mixtures, current density increased and electrical resistance decreased with time. Concretes containing trass cement and ASTM Type II cement with 7% silica fume and (w/cm)=0.35 showed lower current density and higher electrical resistance. For greater cover depth, a tendency of lower negative potential, lower current density, and higher electrical resistance was observed.

Table. 4. Current density and concrete resistance at 1 year, in the tidal region

Mixture	w/cm	Current ($\mu\text{A}/\text{cm}^2$)			Resistance (kohm)		
		3.5cm	5cm	7cm	3.5cm	5cm	7cm
A1	0.40	0.99	0.91	0.64	1.8	1.7	1.6
A2	0.35	0.93	0.81	0.61	2.1	2.6	2.2
B1	0.40	2.97	1.84	0.87	1.0	1.9	1.9
B2	0.35	1.56	1.48	0.66	0.5	2.5	2.6
C1	0.40	0.97	0.88	0.67	1.8	2.0	2.1
C2	0.35	0.95	0.76	0.52	1.6	1.8	1.8
D1	0.40	1.75	1.22	1.12	0.8	1.9	2.1
D2	0.35	0.86	0.90	0.78	1.8	2.3	2.2
E1	0.40	1.97	1.86	1.54	1.4	1.3	1.7
E2	0.35	0.93	0.73	0.68	1.2	2.0	2.0

Table. 5. Current density and concrete resistance at 4 years, in the tidal region

Mixture	w/cm	Current ($\mu\text{A}/\text{cm}^2$)			Resistance (kohm)		
		3.5cm	5cm	7cm	3.5cm	5cm	7cm
A1	0.40	2.84	2.38	2.79	0.8	1.2	1.2
A2	0.35	2.03	1.56	1.22	0.8	1.5	1.7
B1	0.40	3.86	3.11	2.21	0.4	0.5	0.7
B2	0.35	3.25	2.33	2.06	0.5	1.3	1.4
C1	0.40	1.95	2.03	1.96	1.2	1.3	1.3
C2	0.35	1.76	1.66	1.52	1.8	2.1	2.8
D1	0.40	1.90	2.37	1.68	1.1	1.3	1.5
D2	0.35	1.99	1.74	1.55	1.3	1.4	1.8
E1	0.40	2.76	2.12	1.82	0.9	1.4	1.8
E2	0.35	2.72	1.91	1.31	1.0	1.7	2.4

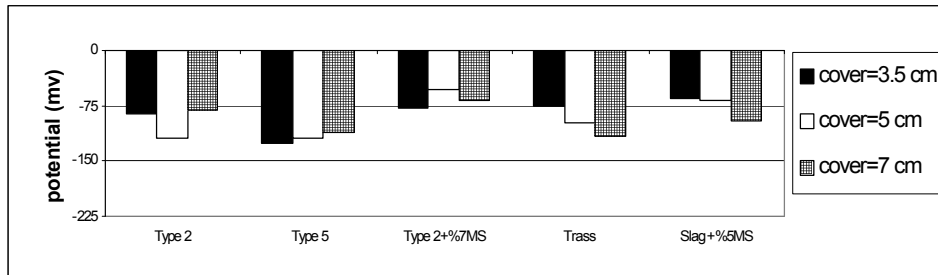


Fig. 2. Half-cell potential at 1 year, $(w/cm)=0.4$, in the tidal region

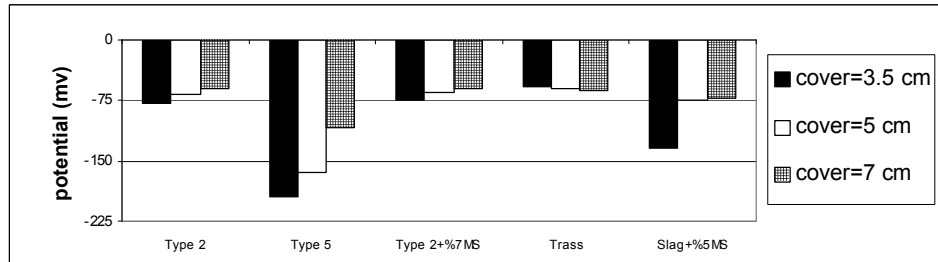


Fig. 3. Half-cell potential at 4 years, $(w/cm)=0.4$, in the tidal region

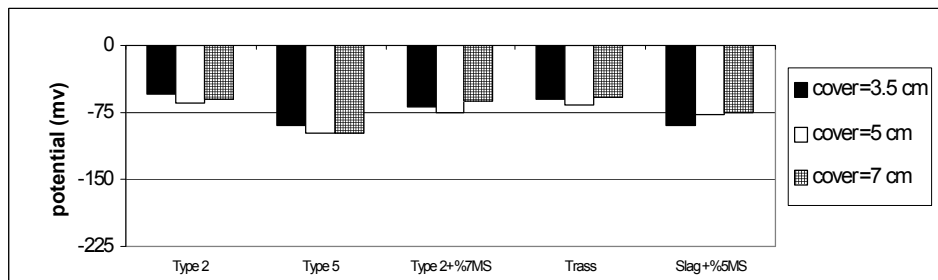


Fig. 4. Half-cell potential at 1 year, $(w/cm)=0.35$, in the tidal region

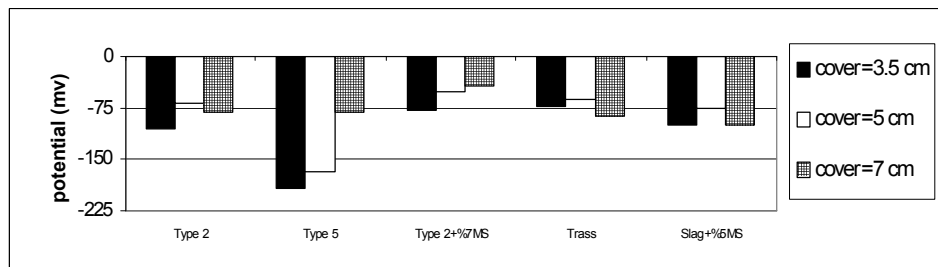


Fig. 5. Half-cell potential at 4 years, $(w/cm)=0.35$, in the tidal region

All concrete mixtures showed no corrosion activity and very low current densities after 48 months of exposure in the air. These concretes showed very significant and high electrical resistances. For the dry exposure condition after 4 years, there were no significant differences in the concrete electrical resistance, corrosion current density and corrosion potential for concrete mixtures made with different cements, for the different cover depths, and various water-cementitious materials ratios.

Table 6. Current density and concrete resistance at 1 year, in the dry condition

Mixture	w/cm	Current ($\mu\text{A}/\text{cm}^2$)			Resistance (kohm)		
		3.5cm	5cm	7cm	3.5cm	5cm	7cm
A1	0.40	1.12	0.77	0.80	2.2	2.7	3.9
A2	0.35	0.53	0.41	0.22	3.9	4.5	4.3
B1	0.40	1.20	0.80	0.60	2.7	3.1	2.8
B2	0.35	0.60	0.54	0.41	4.5	5.5	5.0
C1	0.40	1.10	0.70	0.42	3.5	3.5	4.5
C2	0.35	1.50	0.80	0.36	3.5	4.0	4.0
D1	0.40	1.30	0.55	0.55	3.5	4.1	5.5
D2	0.35	0.72	0.53	0.45	4.0	5.5	5.8
E1	0.40	1.02	0.60	0.45	3.0	5.0	4.6
E2	0.35	0.70	0.70	0.45	5.0	5.0	5.2

Table 7. Current density and concrete resistance at 4 years, in the dry condition

Mixture	w/cm	Current ($\mu\text{A}/\text{cm}^2$)			Resistance (kohm)		
		3.5cm	5cm	7cm	3.5cm	5cm	7cm
A1	0.40	0.25	0.27	0.30	6.0	6.5	6.0
A2	0.35	0.26	0.19	0.22	6.0	6.1	6.1
B1	0.40	0.49	0.35	0.27	4.9	4.8	5.6
B2	0.35	0.38	0.25	0.24	5.2	5.7	5.8
C1	0.40	0.38	0.29	0.24	5.8	5.9	6.1
C2	0.35	0.32	0.28	0.21	6.3	6.5	6.7
D1	0.40	0.31	0.29	0.27	5.8	5.9	6.1
D2	0.35	0.32	0.33	0.25	6.1	6.0	5.9
E1	0.40	0.33	0.32	0.25	5.1	5.4	5.8
E2	0.35	0.22	0.26	0.24	6.0	6.0	6.1

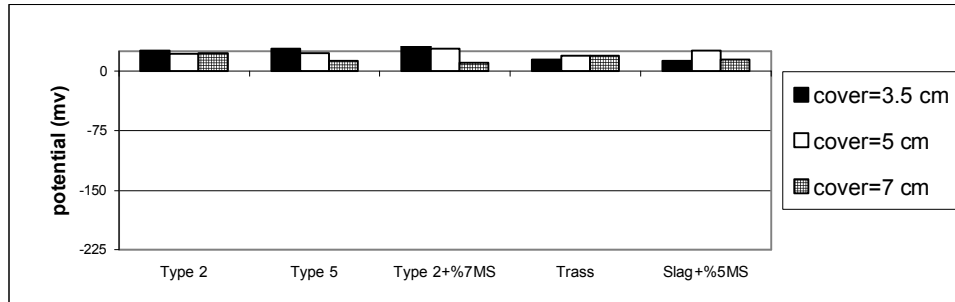


Fig. 6. Half-cell potential at 4 years, (w/cm)=0.4, in the dry condition

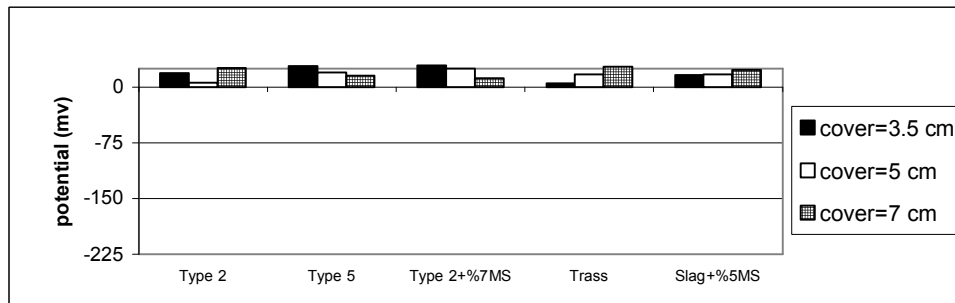


Fig. 7. Half-cell potential at 4 years, (w/cm)=0.35, in the dry condition

For all of the concrete mixtures in a submerged condition and after 12 months, a very high negative potential was observed. However, the current densities were low. The results show that although chloride ions have penetrated into the concrete and have reached the surface of reinforcement, due to the lack of oxygen, there is little micro-cell corrosion. For the wet and submerged condition, no significant difference in performance of concretes with different cements and w/cm was observed.

Table. 8. Current density and concrete resistance, in the submerged condition

Mixture	w/cm	1 years		4 years	
		Current ($\mu\text{A}/\text{cm}^2$)	Resistance (kohm)	Current ($\mu\text{A}/\text{cm}^2$)	Resistance (kohm)
		7cm		7cm	
A1	0.40	1.52	1.2	1.37	2.1
A2	0.35	1.15	2.0	0.85	1.7
B1	0.40	1.87	1.1	1.39	0.8
B2	0.35	1.95	1.2	0.85	1.0
C1	0.40	0.75	1.5	0.82	1.3
C2	0.35	0.40	2.2	0.76	1.7
D1	0.40	0.90	1.3	1.45	1.1
D2	0.35	1.00	1.6	1.31	1.4
E1	0.40	1.25	1.9	1.13	1.6
E2	0.35	1.10	2.2	0.82	2.0

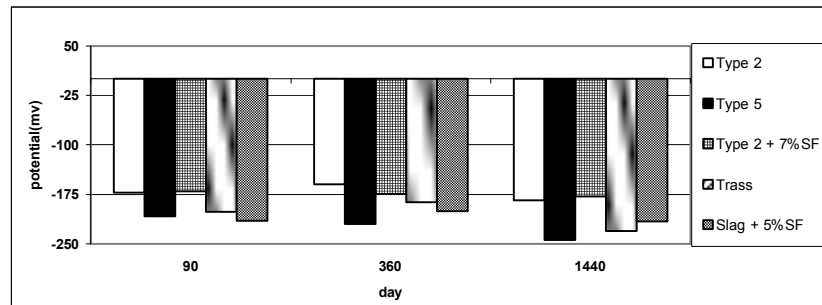


Fig. 8. Half-cell potential versus age ; (w/cm)=0.35,cover=7cm, submerged condition

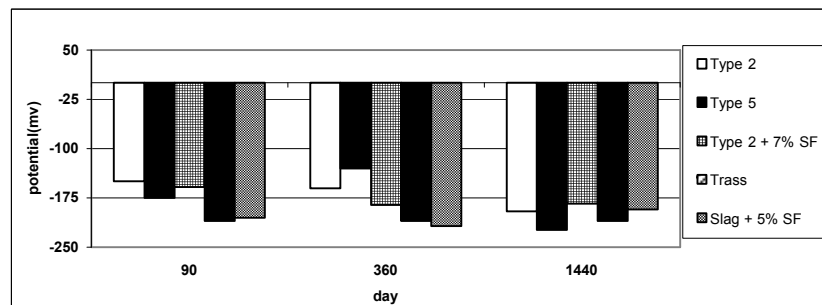


Fig. 9. Half-cell potential versus age ; (w/cm)=0.4,cover=7cm, submerged condition

4-2- Carbonation Depth and Chloride-ion Diffusion

In the tidal region and dry condition, carbonation depth of specimens were negligible irrespective of the types of cement. In the tidal region, for all concrete mixtures, higher chloride-ion concentration was observed at the surface after 1 year. However it was reduced to a negligible value at deeper depths (see Figs. 10 and 11). Mixtures of type V Portland cement show the highest chloride content. Mixtures made with containing pozzolanic cement and type II Portland cement with 7% silica fume exhibit the lowest chloride content.

Comparison of Chloride content of specimens in the tidal zone showed that type V Portland cement mixtures with water-cement ratio of 0.4 showed the worst performance.

This data complies with the results obtained in intensity and potential of concrete mixtures. It also reveals that corrosion of reinforcement should have been occurred in such mixtures. In order to clarify the corrosion condition, concrete specimens made with type V Portland cement were tested after four years. Fig. 12 shows the chloride profile of the concrete mixture. It is clearly seen that the amount of chlorides at the reinforcement level is well above the threshold level. Heavily corroded bars were observed when broken specimens were visually inspected. Fig. 13 shows the severe corrosion of the bars in concrete mixtures made with type V Portland cement. Performance of mixtures containing type II Portland cement with 7% silica fume and slag cement mixtures with 5% silica fume was better in controlling chloride diffusion than the other concrete mixtures.

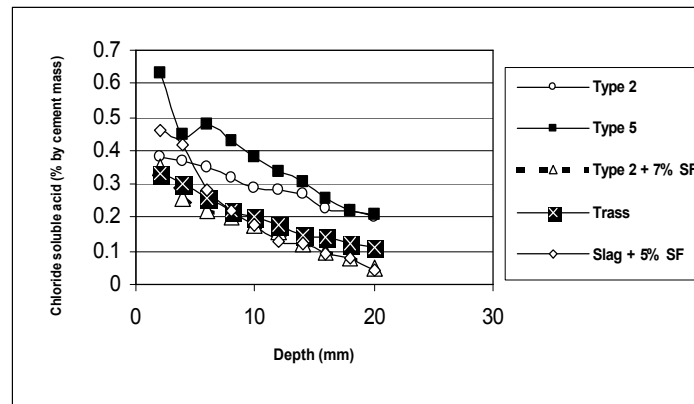


Fig. 10. Profile of acid soluble chloride ion concentrations, (w/cm)=0.4, in the tidal region at 1 year

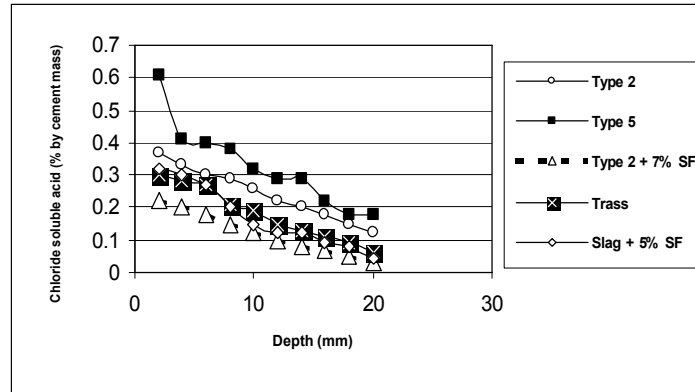


Fig. 11. Profile of acid soluble chloride ion concentrations, $(w/cm)=0.35$, in the tidal region at 1 year

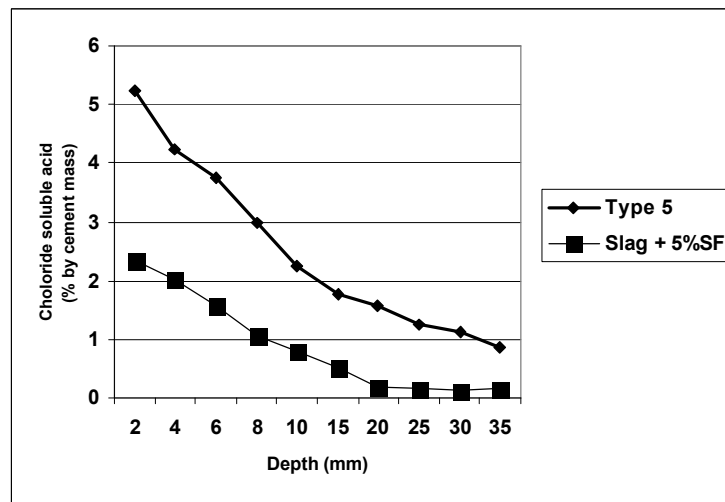


Fig. 12. Profile of acid soluble chloride ion concentrations, $(w/cm)=0.40$, in the tidal region at 4 years



Fig. 13. Heavy corroded reinforcement in concrete made with Type V Portland cement after 4 years

4-3- Compressive Strength and Permeability

Compressive strength test results for concrete mixtures under standard curing conditions are shown in Figs. 14 and 15. It can be seen that the compressive strength of all concrete mixtures is above 60 Mpa at 4 years, regardless of w/cm ratio. Higher compressive strengths are expected at later ages for concretes containing pozzolans.

Relatively higher strength was observed in the case of ASTM Type V and Type II Portland cement concrete mixtures when compared with Trass, Type II + Silica fume and Slag cement mixtures. However, concrete mixtures containing ASTM Type V Portland cement showed undesirable performance in terms of corrosion.

Permeability under water pressure for all concrete mixtures was low irrespective of the type of cement and water-cement ratios used in this investigation.

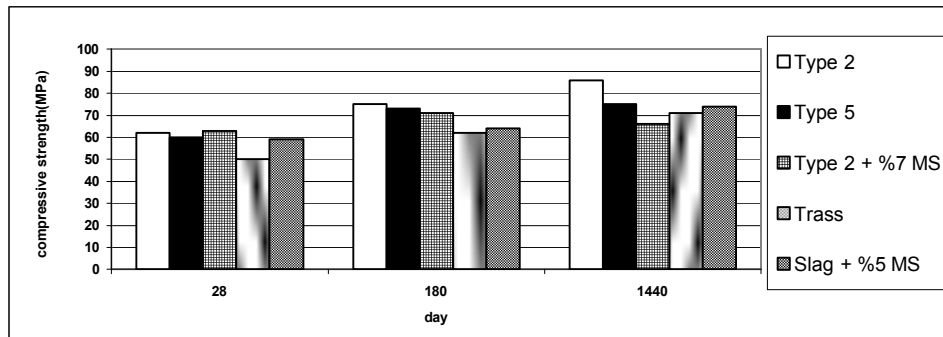


Fig. 14. Compressive strength of concrete versus age ; (w/cm=0.35)

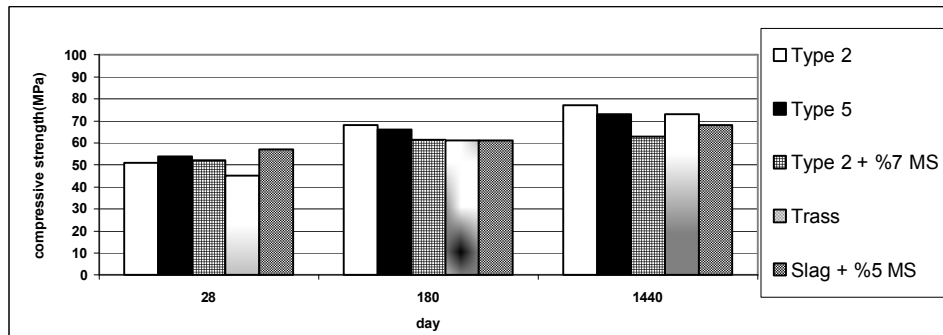


Fig. 15. Compressive strength of concrete versus age ; (w/cm=0.4)

5- CONCLUSIONS

From the results obtained in this investigation, the following conclusions can be drawn:

- 1- For specimens exposed to the tidal region, concrete mixtures made with Type V Portland cement having 3.5 and 5 cm cover thicknesses showed undesirable performance. Severe reinforcement corrosion was

observed in the specimens after 4 years. The best performance was obtained for concrete mixtures containing Trass cement and ASTM Type II Portland cement plus silica fume.

- 2- In totally submerged specimens, although corrosion potential is high and concrete electrical resistance is low, current density is negligible after 4 years. No corrosion observed in all concrete mixtures.
- 3- All concrete mixtures showed no activity and very low current densities after 4 years of exposure in air. These concretes showed high electrical resistances. For this exposure condition, there was no significant difference in the performance of concrete mixtures made with different cements and for various cover thicknesses.
- 4- In general, exposure in the tidal region was the worst condition for concrete mixtures when compared with the submerged and dry conditions.

6- REFERENCES

- [1] Ramezani pour, A.A., Miyamoto, A., "Durability of concrete structures in the Persian Gulf", Concrete journal, Japan Concrete Institute, Vol 18, No. 3, March 2000
- [2] Mohammed, T.u., Yamaji, T., Toshiyuki, A., and Hamada, H., "Corrosion of steel bars in cracked concrete made with ordinary Portland, Slag and Fly Ash Cement", Proceedings of the 7th CANMET/ACI International Conference on Fly Ash, Silica Fume, and Natural Pozzolans in Concrete, Madras, India, July 2001
- [3] Mohammed, T.u., Otsuki, N., Hisada, M., Hamada, H., "Marine durability of 23-Year-old reinforced concrete beams", Fifth CANMET/ACI International Conference on Durability of Concrete, Barcelona, Spain, ACI SP 192-65, 2000, PP. 1071-1088
- [4] Rasheeduzzafar, A.S., Dakhil, S.S., Al-Gahtani, A.S., "Effect of cement composition on corrosion of reinforcing steel in concrete", Third International Symposium on Corrosion of Reinforcement in Concrete Construction, U.K., Edited by Page, C.L., 1995, PP. 213-226
- [5] Ramezani pour, A.A., Hillemeier, B., Pourkhorshidi, A.R., Parhizkar, T. and Raies Ghasemi, A.M., "Performance of pozzolanic cement concretes in hot and aggressive environments", 7th International Conference on Concrete in Hot and Aggressive Environments, Bahrain, October 2003
- [6] Ramezani pour, A.A., Radfar, Moslehi, Maghsoodi, "Performance of different pozzolanic cement concretes under cyclic wetting and drying", 6th CANMET/ACI International Conference on Fly ash, Silica fume, Slag and Natural Pozzolans in Concrete, ACI SP 178-39, 1998, PP. 759-777.
- [7] Ramezani pour, A.A., Ashrafi H.R., Ramezani pour, A.M., "Chloride diffusion models for Persian Gulf environments", Third International Conference on Construction Materials, ConMat05, August 2005, Vancouver, Canada

[8] Ramezaniapour, A.A., Pourkhorshidi, A.R., "Durability of concrete containing supplementary cementing materials under hot and aggressive environments", Proceeding of 8th CANMET/ACI International Conference on Fly ash, Silica fume, Slag and Natural Pozzolans in Concrete, May 2004, Las Vegas, U.S.A.